

## DRUG DELIVERY SYSTEMS IN UROLOGY— GETTING “SMARTER”

OMID C. FAROKHZAD, JORDAN D. DIMITRAKOV, JEFFREY M. KARP, ALI KHADEMHSSEINI,  
MICHAEL R. FREEMAN, AND ROBERT LANGER

**U**rology holds the most enviable position in the medical firmament. Unique among specialties in bringing the surgeon in contact with humans throughout the spectrum of human life—from newborn to geriatric patients—urologists need to be adept at both medical and surgical therapies alike. In this context, drug delivery in urology has had a long, and sometimes far from illustrious, history. Traditionally, many genitourinary conditions have been treated with medications administered orally, which requires larger doses, with the concomitant side effects. The popularity of localized delivery systems, in contrast, has been determined by the ease of system implantation, objective treatment efficacy, patient-reported treatment satisfaction, and observed side effects.

The genitourinary tract presents a unique opportunity for local drug delivery. The kidney, bladder, and prostate are easily accessible for minimally invasive interventions. Nanoparticles, microparticles, or small-scale implants can simply be deployed and retrieved using percutaneous or endoscopic systems in outpatient settings with minimal patient discomfort and maximal therapeutic benefit. This review describes genitourinary therapies of the past, present, and future, with par-

ticular emphasis on the emerging state-of-the-art biopolymer and drug delivery systems in urology and their potential to shape the future of urologic science and practice.

### LIMITATIONS OF CURRENT THERAPEUTIC APPROACHES

#### INTRAVESICAL TREATMENTS

Molecular weight, polarity, concentration, exposure time, and urothelial surface alterations have been proposed as the major factors determining the rate of transurothelial drug absorption.<sup>1</sup> The ideal intravesical agent has been postulated to have negligible ionization between pH 6 and 7, a molecular weight greater than 200 amu, and a partition coefficient in the critical ranges of either −0.4 to −0.2 or −7.5 to −8.0.<sup>2</sup> The importance of these factors is underscored by the results of a recent Phase III randomized clinical trial for intravesical mitomycin. Eliminating the residual volume, overnight fasting, doubling the mitomycin concentration to 40 mg in 20 mL, and urinary alkalinization using oral bicarbonate (to reduce mitomycin degradation) resulted in a doubling of the durable tumor-free rate at 5 years.<sup>3</sup>

As is the case with intravesical mitomycin, acidic urinary pH is also the limiting factor in intravesical doxorubicin and epirubicin therapy. Alkalization with gamma linolenic acid has been shown to increase epirubicin efficacy. Additional enhancement has been reported after verapamil administration.

Another major determinant of therapeutic success is the degree of drug lipophilicity, which allows penetration through cell membranes. For example, paclitaxel, a highly lipophilic compound, achieves greater intraurothelial concentrations than either mitomycin or doxorubicin. However, its poor urine solubility presents unique challenges for intravesical administration. Moreover, Cremophor (polyoxyethylated castor oil), a stabilizing agent used in the Food and Drug Administration-approved formulation (Taxol), reduces the pacli-

*This work was supported by National Institutes of Health/National Institute of Arthritis, Diabetes, Digestive and Kidney Diseases grant R01 DK 065990 to J. D. Dimitrakov and in part by the Koch Research Fund, National Institutes of Health grants CA119349, EB003647, and HL60435, the Draper Laboratory, and the Institute of Soldier Nanotechnology (DAAD-19-02-D-002). J. M. Karp was supported by a Natural Sciences and Engineering Research Council of Canada fellowship.*

*From the Departments of Anesthesiology and Medicine, Brigham and Women's Hospital; Harvard Medical School; Harvard Urological Diseases Research Center, Children's Hospital, Boston, Massachusetts; Department of Chemical Engineering and Harvard-MIT Division of Health Sciences and Technology, Massachusetts Institute of Technology, Cambridge, Massachusetts*

*Reprint requests: Jordan D. Dimitrakov, M.D., Ph.D., Harvard Urological Diseases Research Center, Enders Research Building, Room 1061, 300 Longwood Avenue, Boston, MA 02115. E-mail: Jordan.Dimitrakov@childrens.harvard.edu*

*Submitted: December 15, 2005, accepted (with revisions): March 28, 2006*

taxel-free fraction by entrapping it in micelles and lowering drug penetration in bladder tissue. Paclitaxel bioavailability can be increased using surface-active agents (eg, dimethyl sulfoxide)<sup>4</sup> to release the agent from the micelles, using a glyceryl monooleate bioadhesive drug delivery system, or nanoparticle encapsulation.

Gemcitabine is an attractive candidate for the ideal intravesical agent. Its molecular weight of 300 amu allows optimal urothelial penetration and minimal systemic absorption. Gemcitabine has a pKa of 3.6, and its reconstitution results in a solution with a pH of 2.7 to 3.2. This favors negligible drug ionization at the usual urinary pH of 6.0 to 7.0 and enhances drug activity. A recent Phase II clinical trial of 2000 mg gemcitabine administered once a week for 6 weeks showed a lack of side effects in 81.3% of the patients, with a disease-free rate of 74.6% at 12 months.<sup>5</sup>

#### INTRAPROSTATIC TREATMENTS

Intraprostatic drug administration has long been considered an attractive alternative for treating prostatic diseases ranging from infection to cancer. Although Brodie first recommended “puncture of the prostate” through the perineum in the treatment of prostatic abscess, Stoll is credited with performing the first intraprostatic injection in 1877. Although a detailed discussion of intraprostatic drug kinetics and distribution is beyond the scope of the present report, Wientjes *et al.*<sup>6</sup> have provided an excellent recent review. It is, however, important to emphasize that the easy accessibility of the prostate, coupled with its slow perfusion rate (16 mL/min/100 g) favors drug entrapment and ensures high concentrations inside the gland after direct intraprostatic delivery. According to the model proposed by Partin and Rodriguez,<sup>7</sup> intraprostatic drug penetration is dependent on drug lipophilicity and nonionic diffusion through cellular membranes. Once the agent reaches the acidic prostatic fluid, it becomes protonated and acquires a more positive charge, with charged drugs becoming relatively trapped within the prostatic secretions. Therefore, the major determining factors for successful penetration are the pKa and protein-binding ability of the drug and the pH of the prostatic secretions. The pH of human prostatic secretions varies greatly from 6 to 8 (mean 6.6). Prostatic inflammation presents a special therapeutic challenge because the pH tends to be 7 or more. Thus, antibacterial agents that have in vitro activity might be inactive in the alkaline prostatic milieu.<sup>7</sup>

#### NOVEL DRUG DELIVERY APPROACHES

Recent advances in materials science, biomaterial development, and tissue engineering are

changing the face of medicine.<sup>8</sup> Biopolymers and drug delivery systems provide the conceptual framework for improving the efficacy of existing drug formulations and developing new treatments.<sup>8,9</sup> Specifically, extensive research has been done in the area of biodegradable materials for controlled release of drugs, which obviates the need for removal of nondegradable drug-depleted devices. Many biodegradable polymers have been evaluated for their suitability as a matrix for drugs, including polyesters, polycarbonates, natural and synthetic polyamides, polyphosphate esters, polyphosphazenes, and polyanhydrides. These polymers may be used in a variety of devices, including biodegradable polymer shape-memory stents, “smart” hydrogel-based systems, nanoparticle-aptamer conjugates, and miniaturized drug delivery devices.


#### Biodegradable Shape-Memory Polymers

The advent of biodegradable shape-memory polymers ushered in a new era of unlimited endoscopic possibilities.<sup>10,11</sup> Biodegradable shape-memory polymers possess the ability to “memorize” a permanent shape that can differ substantially from their initial temporary shape. Thus, bulky devices can be introduced endoscopically in a compressed temporary shape (eg, a “coil”) that can then be expanded on demand into a permanent shape (eg, a “rod”; Fig. 1). Additionally, these polymers can be engineered into sutures that possess the ability to tie themselves (see Supplementary Video) on demand as a result of a temperature shift (eg, from room to body temperature).

In urology, these materials hold the promise for developing degradable drug-eluting stents.<sup>12</sup> Initially, at room temperature, a shape-memory stent could be delivered endoscopically in a compressed state. When the temperature increases to that of the human body (ie, greater than the switching transition temperature of the polymer), the stent will expand into a coil.<sup>10</sup> Biodegradable stents obviate the need for repeat interventions for removal<sup>13</sup> and can serve as reservoirs of active agents (eg, antibiotics, alkalinizing agents), which can bulk the device and be released from the surface.

#### “Smart Gels”

Histrelin-eluting hydrogel implants have been shown to effectively suppress testosterone for longer than 1 year in patients with prostate cancer.<sup>14</sup> Furthermore, hydrogels have been used as oligonucleotide-releasing vehicles in the kidney.<sup>15</sup> During the past two decades, hydrogels have been developed as “smart” carriers in controlled drug delivery systems.<sup>16</sup> Their physical and chemical properties have been engineered at the molecular level to optimize their properties, such as perme-

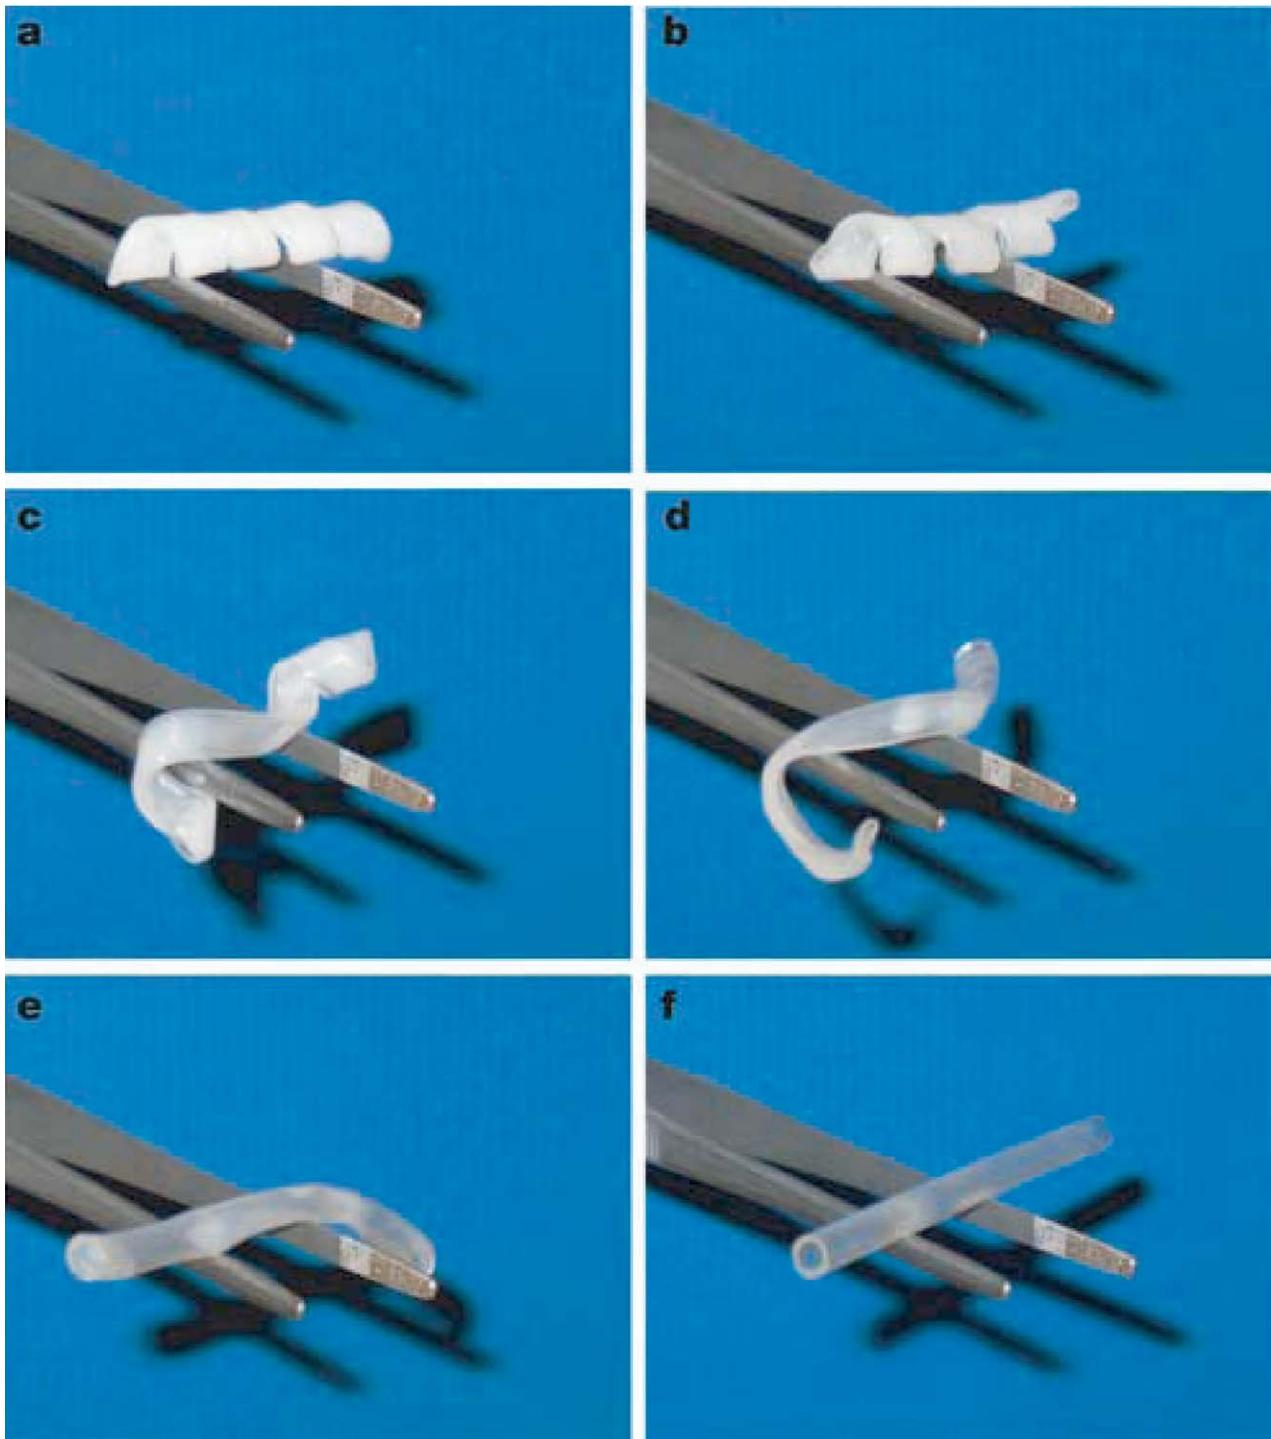


**FIGURE 1.** Time series of photographs showing recovery of shape-memory tube. (a-f) Start to finish of process: total time 10 seconds at 50°C. Tube was made of poly(epsilon-caprolactone) dimethacrylate polymer network that had been programmed to form a flat helix. Reprinted by permission from McMillan Publishers Ltd: [Langer R, and Tirrell DA: Designing materials for biology and medicine. *Nature* 428: 487–492, 2004, copyright 2004]; <http://www.nature.com/nature/index.html>.

ability (eg, sustained release applications), environmentally responsive nature (eg, pulsatile release applications), surface functionality (eg, polyethylene glycol coatings for stealth release), biodegradability (eg, bioreversible applications),

and surface biorecognition sites (eg, targeted release and bioadhesion applications).

Environmentally responsive hydrogels have been used for a variety of controlled drug delivery applications. The “smart” component of these sys-

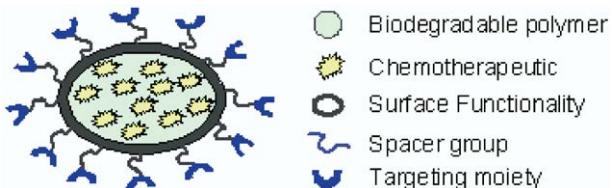

**FIGURE 2.** Design of nanoparticle-drug conjugates involves combining drug laden materials, such as biodegradable polymers, with targeting moiety. Polymer should have functional groups for attachment of targeting moieties (which can be bound directly to surface or through a spacer group) and molecules to enhance half-life in circulation [ie, poly(ethylene glycol)].

tems allows for release of drugs in response to changes in the surrounding environment. For example, thermal-responsive hydrogels have been used for sustained intravesical drug delivery.<sup>17,18</sup> pH-responsive hydrogels composed of polyethylene glycol-containing ionic networks have been used for protein delivery (eg, insulin).<sup>19</sup> Furthermore, by exhibiting control over cross-linking and swelling properties, hydrogels can be programmed to trigger drug release.<sup>20</sup> These properties have been used in poly(vinyl alcohol) and polyethylene glycol systems in which the density and degree of network cross-linking can be regulated by modifying the polymer chain length, polymer composition, and initiation concentration, among other factors.<sup>21</sup>

Drug delivery systems responsive to biologic analytes can be developed by incorporating enzymes within environmentally responsive hydrogels (eg, glucose-responsive hydrogels incorporating glucose).<sup>22</sup> Their release kinetics make them useful as “smart” materials for diabetes applications, or, in the case of incontinence, these gels can provide “remote control” and ongoing readjustment of implants.

#### TARGETED NANOPARTICLES

One approach aimed at minimizing the adverse effects of current chemotherapeutic agents and enhancing the survival of patients with metastatic cancer involves drug targeting to cancer cells through tumor-specific antigens (eg, prostate-specific membrane antigen [PSMA]) and direct intracellular cytotoxic agent release for an extended period.<sup>23,24</sup> This goal can be achieved through combining controlled-release technology and targeted drug delivery approaches. With advances in nanotechnology, it is now possible to develop highly selective and effective cancer therapeutics by combining specialized biomaterials with available chemotherapeutic agents.<sup>25</sup> An emerging promising strategy involves the delivery of drug-laden nanoparticles conjugated to targeting mo-

ieties<sup>23,24</sup> (Fig. 2). One major clinical advantage of such nanoparticle-drug conjugates over conventional drugs is the specific delivery of large amounts of chemotherapeutic agents per recognition event. In choosing effective targeting moieties, one must consider their ability to exhibit high specificity and affinity for the target molecule.

A recent genomics-based approach for identifying cancer-specific antigens suitable for targeted therapy demonstrated high levels of E-selectin expression in prostate cancer epithelium. On the basis of this finding, an E-selectin-targeting antibody drug conjugate was constructed that showed great potential in a mouse prostate cancer model.<sup>26</sup>

Antibody-based treatment strategies against several target antigens (eg, Her-2/neu, epidermal growth factor receptor, and PSMA) have been successfully used in urology.<sup>27</sup> A recent Phase I trial of <sup>177</sup>lutetium-labeled J591, a monoclonal antibody to PSMA, in patients with androgen-independent prostate cancer demonstrated the efficacy of this treatment approach.<sup>28</sup> Another promising approach is the use of MLN2704, a de-immunized, PSMA-targeted monoclonal antibody conjugated to drug maytansinoid 1, a microtubule-depolymerizing compound.<sup>29</sup> Additionally, drug targeting can be accomplished through conjugation of molecules (eg, antibodies or peptides) to nanoparticles. Although peptide-based molecules may be an effective mode of delivery, a potential disadvantage of this approach lies in the challenges involved in monoclonal antibody production. For example, the target antigen may not be well tolerated by the animal used to produce the antibodies, or the target molecules may be inherently less immunogenic, making it difficult to raise antibodies against such targets (although this problem can be overcome with the use of phage display libraries).<sup>30,31</sup>

A strategy that aims to overcome some of these limitations is the use of aptamers for the delivery of controlled-release polymer systems. Nucleic acid ligands (aptamers) are a novel class of ligands<sup>32,33</sup> that have the potential to rival current antibody-based targeting approaches.<sup>34,35</sup> Aptamers are short, single-stranded DNA or RNA oligonucleotides that have been selected *in vitro* from a large number of random sequences ( $\sim 10^{14}$  to  $10^{15}$ ) and have a molecular weight of 10 to 15 kD, one order of magnitude lower than that of antibodies (150 kD).<sup>36</sup> Aptamers bind to their targets with high affinity and specificity, have a high inhibitory potential, are not toxic or immunogenic, and can be produced synthetically. They can discriminate between closely related isoforms or different conformational states of the same target and can recognize murine and human protein targets with equal affinities, making them suitable for both preclinical and clinical development. In contrast to anti-

bodies, aptamers bind to functional domains of the target protein (eg, substrate binding pockets or allosteric sites), thereby modulating the biologic function of the molecule. Aptamers usually retain their binding and inhibitory behavior even after immobilization on carrier material, delivery into animals, labeling with various functional groups, or when expressed within cells. Aptamers are derived from an *in vitro* iterative protocol (*in vitro* selection<sup>32</sup> or systematic evolution of ligands by exponential enrichment).<sup>33</sup> In addition, any specific targeting aptamer may be tailor-made, provided that a small quantity of pure target is available. Although the total number of targets is largely unknown, the systematic evolution of ligands by exponential enrichment system may be successfully modified using a variety of approaches to overcome these limitations. For example, it is possible to incorporate selection by intact biologic entities such as cancer cells or tissues to identify an array of highly specific aptamers.<sup>37,38</sup>

A major limitation of current loss-of-function technologies (gene knockout, antisense oligonucleotides, or RNA interference) is their dependence on genetic inactivation at the genomic or transcriptional level. The use of antibodies as target validation tools is limited to extracellular targets, because the reducing intracellular environment hampers the application of antibodies inside the cells. In this respect, aptamers offer a unique advantage, because they have a low molecular weight, can be used for intracellular studies, and can be labeled with fluorophores or nanoparticles for localization experiments. Furthermore, aptamers inhibit their targets by competitive and non-competitive mechanisms. This unique property allows the study of different inhibitory mechanisms or posttranslational conformations of target proteins in protein networks without altering the proteomic status of the model system.

We have recently demonstrated, *in vitro*, a proof of concept for nanoparticle-aptamer bioconjugates that target PSMA on the surface of prostate cancer cells and get taken up by cells that express the PSMA protein specifically and efficiently.<sup>23</sup> We have also shown, using a microfluidic system, that these aptamers are suitable for targeted drug delivery<sup>24</sup> and have recently demonstrated the *in vivo* efficacy of nanoparticle-aptamer conjugates using a xenograft prostate cancer mouse model.<sup>39</sup>

#### MINIATURIZED DRUG DELIVERY DEVICES

Microscale and nanoscale devices are attractive platforms for urologic therapies. Microscale approaches, such as microfluidics, microdevices, and micropatterning, provide a particularly useful method of delivering molecules to various tissues of the body.<sup>40,41</sup> These technologies, known as mi-


croelectromechanical systems (MEMSs), originated in the semiconductor and microelectronics industry in microchip fabrication. MEMS technology has been used in sensing chemicals, performing microsurgery, and delivering drugs. To create MEMS devices capable of releasing drugs, typically top-down nanofabrication and microfabrication methods, such as photolithography or soft lithography, have been used.

In photolithography, a mask is aligned above a thin film of a photo-responsive material, termed photoreist. Microstructures can then be generated by shining the ultraviolet light on particular regions of a substrate.<sup>42</sup> Although photolithography has been widely used in microelectronics, it has a number of disadvantages, including the high costs associated with photolithographic equipment (aligners and spinners) and clean room use, as well as the chemically harsh conditions that are not compatible with biomolecules. To alleviate these challenges, a set of alternative techniques collectively known as soft lithography has been developed to fabricate functional structures with dimensions in the range of tens of nanometers to hundreds of micrometers.<sup>42</sup> Soft lithographic approaches commonly use a microstructured surface made with elastomeric polymers such as poly(dimethylsiloxane). Poly(dimethylsiloxane) is optically transparent, permeable to gases, elastomeric, and durable, making it also suitable for cell applications. By using a micromolding process, soft lithographic approaches minimize the amount of clean room time and equipment needed.


MEMS technology has great potential in various urologic diagnostic applications such as pressure sensors and micropumps.<sup>43</sup> The seminal research on the use of MEMS technology for drug delivery was performed using microchips that were designed to release complex profiles of multiple drugs. These systems exist in a nondegradable “active”<sup>40,41,44</sup> (Fig. 3) and a degradable “passive”<sup>45,46</sup> (Fig. 4) format.

The active format (Fig. 3) is constructed from a silicon wafer containing multiple microscale reservoirs that can be opened to release drugs through electrochemical dissolution of a thin gold membrane (anode) that covers the microreservoirs. The release of the drug, which can be stored in solid, liquid, or gel form, is initiated by applying an electric potential of approximately 1 V between the anode membrane and the cathode to any individual reservoir. The cathode remains intact during this process, but the anode dissolves owing to a reaction between it and the salt solution in which it is immersed.

Alternatively, the passive format (Fig. 4) is made from poly(lactic acid) and is fully resorbable, with reservoirs covered with thin biodegradable membranes. By using various types of polymers or copol-

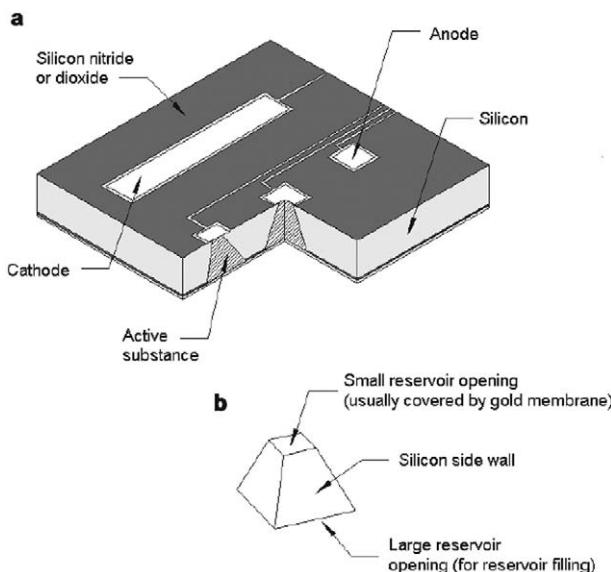

**FIGURE 3.** Nondegradable microchip device for pulsatile release of multiple substances. Reprinted by permission from McMillan Publishers Ltd: [Santini JT Jr, Cima MJ, and Langer R: A controlled-release microchip. *Nature* 397: 335–338, 1999, copyright 1999]; <http://www.nature.com/nature/index.html>.

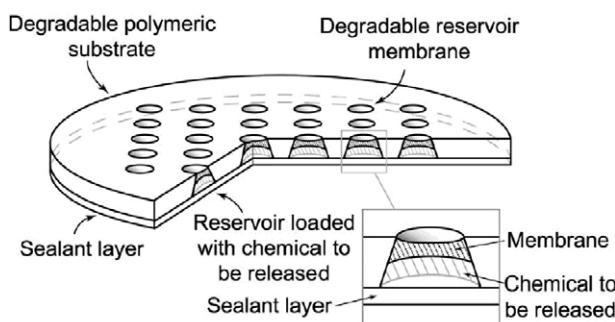

**FIGURE 4.** Degradable microchip device for pulsatile release of multiple substances. Reprinted by permission from McMillan Publishers Ltd: [Richards Grayson AC, Choi IS, Tyler BM, et al: Multi-pulse drug delivery from a resorbable polymeric microchip device. *Nat Mater* 2: 767–772, 2003, copyright 2003]; <http://www.nature.com/nmat/index.html>.

ymers with a variety of molecular weights, the microchip systems can be programmed to degrade at set times after implantation. The current development in the use of this technology is to incorporate control elements such as pumps and sensors that can release drugs in response to external stimuli. It is envisioned that through their capability to deliver multiple drugs at desired doses, microchip drug delivery devices will be useful vehicles that can be either implanted or injected for urologic applications.

Microfabricated technologies have also been developed to deliver drugs to a target site using microfabricated silicon or biodegradable microneedles. Although the main application of these

delivery vehicles has been for transdermal delivery, it is envisioned that by using microfabricated techniques, it will be possible to generate self-contained devices that can be deposited cystoscopically into the bladder and be used as drug delivery reservoirs. A similar approach has been developed by creating asymmetric microfabricated vehicles.<sup>47</sup> These have been extensively used as bioadhesives and may be used for localized drug delivery inside the bladder (eg, for paclitaxel).

Another mode of drug delivery that may be suitable for urologic application is the fabrication of micropumps for intrarenal and intraprostatic delivery. Micropumps may be used to deliver medication for treating diseases such as uric acid nephrolithiasis. Most of the existing methods of delivering fluids are based on silicon technology.<sup>48</sup> Although silicon has the added benefit of being well-studied, it is rigid and may not be suitable for some delivery applications. Therefore, flexible microchannels made from novel materials (eg, parylene) could be used to fabricate flexible probes and delivery tools for specific urologic applications.<sup>49,50</sup> These flexible microfluidics can transfer fluids within the body along a narrow path without the damaging effects of a rigid object.

## CONCLUSIONS

Advances in material science are shaping the future of urologic clinical practice. With drug delivery technology maturing, the application of nanodevices in urology will provide methods of addressing current clinical challenges, ultimately leading to mainstream therapies.

## REFERENCES

1. Lum B: Intravesical chemotherapy of superficial bladder cancer, in Torti F (Ed): *Urologic Cancer: Chemotherapeutic Principles and Management*. Berlin, Springer-Verlag, 1983, pp 3–36.
2. Mishina T, Watanabe H, Kobayashi T, et al: Absorption of anticancer drugs through bladder epithelium. *Urology* 27: 148–157, 1986.
3. Au JL, Badalament RA, Wientjes MG, et al: Methods to improve efficacy of intravesical mitomycin C: results of a randomized phase III trial. *J Natl Cancer Inst* 93: 597–604, 2001.
4. Chen D, Song D, Wientjes MG, et al: Effect of dimethyl sulfoxide on bladder tissue penetration of intravesical paclitaxel. *Clin Cancer Res* 9: 363–369, 2003.
5. Bartoletti R, Cai T, Gacci M, et al: Intravesical gemcitabine therapy for superficial transitional cell carcinoma: results of a phase II prospective multicenter study. *Urology* 66: 726–731, 2005.
6. Wientjes MG, Zheng JH, Hu L, et al: Intraprostatic chemotherapy: distribution and transport mechanisms. *Clin Cancer Res* 11: 4204–4211, 2005.
7. Partin A, Rodriguez R: The molecular biology, endocrinology, and physiology of the prostate and seminal vesicles, in Walsh PC, Retik AB, Vaughan ED Jr, et al (Eds): *Campbell's Urology*, 8th ed. Philadelphia, WB Saunders, 2002, pp 1237–1297.

8. Langer R, and Tirrell DA: Designing materials for biology and medicine. *Nature* **428**: 487–492, 2004.
9. Langer R: Drug delivery and targeting. *Nature* **392**: 5–10, 1998.
10. Lendlein A, and Langer R: Biodegradable, elastic shape-memory polymers for potential biomedical applications. *Science* **296**: 1673–1676, 2002.
11. Venkatraman SS, Tan LP, Joso JF, et al: Biodegradable stents with elastic memory. *Biomaterials* **27**: 1573–1578, 2006.
12. Brauers A, Thissen H, Pfannschmidt O, et al: Development of a biodegradable ureteric stent: surface modification and in vitro assessment. *J Endourol* **11**: 399–403, 1997.
13. Auge BK, Ferraro RF, Madenjian AR, et al: Evaluation of a dissolvable ureteral drainage stent in a swine model. *J Urol* **168**: 808–812, 2002.
14. Dineen MK, Tierney DS, Kuzma P, et al: An evaluation of the pharmacokinetics and pharmacodynamics of the histrelin implant for the palliative treatment of prostate cancer. *J Clin Pharmacol* **45**: 1245–1249, 2005.
15. Ramakumar S, Phull H, Purves T, et al: Novel delivery of oligonucleotides using a topical hydrogel tissue sealant in a murine partial nephrectomy model. *J Urol* **174**: 1133–1136, 2005.
16. Peppas N: Hydrogels and drug delivery. *Curr Opin Colloid Interf Sci* **2**: 531–537, 1997.
17. Tyagi P, Chancellor MB, Li Z, et al: Urodynamic and immunohistochemical evaluation of intravesical capsaicin delivery using thermosensitive hydrogel and liposomes. *J Urol* **171**: 483–489, 2004.
18. Tyagi P, Li Z, Chancellor M, et al: Sustained intravesical drug delivery using thermosensitive hydrogel. *Pharm Res* **21**: 832–837, 2004.
19. Morishita M, Lowman AM, Takayama K, et al: Elucidation of the mechanism of incorporation of insulin in controlled release systems based on complexation polymers. *J Control Release* **81**: 25–32, 2002.
20. Peppas N, and Langer R: Origins and development of biomedical engineering within chemical engineering. *Aiche J* **50**: 536–546, 2004.
21. Stringer JL, and Peppas NA: Diffusion of small molecular weight drugs in radiation-crosslinked poly(ethylene oxide) hydrogels. *J Control Release* **42**: 195–202, 1996.
22. Podual K, Doyle FJ III, and Peppas NA: Glucose-sensitivity of glucose oxidase-containing cationic copolymer hydrogels having poly(ethylene glycol) grafts. *J Control Release* **67**: 9–17, 2000.
23. Farokhzad OC, Jon S, Khademhosseini A, et al: Nanoparticle-aptamer bioconjugates: a new approach for targeting prostate cancer cells. *Cancer Res* **64**: 7668–7672, 2004.
24. Farokhzad OC, Khademhosseini A, Jon S, et al: Microfluidic system for studying the interaction of nanoparticles and microparticles with cells. *Anal Chem* **77**: 5453–5459, 2005.
25. Ferrari M: Cancer nanotechnology: opportunities and challenges. *Nat Rev Cancer* **5**: 161–171, 2005.
26. Bhaskar V, Law DA, Ibsen E, et al: E-selectin up-regulation allows for targeted drug delivery in prostate cancer. *Cancer Res* **63**: 6387–6394, 2003.
27. Palapattu GS, and Reiter RE: Monoclonal antibody therapy for genitourinary oncology: promise for the future. *J Urol* **168**: 2615–2623, 2002.
28. Bander NH, Milowsky MI, Nanus DM, et al: Phase I trial of <sup>177</sup>lutetium-labeled J591, a monoclonal antibody to prostate-specific membrane antigen, in patients with androgen-independent prostate cancer. *J Clin Oncol* **23**: 4591–4601, 2005.
29. Henry MD, Wen S, Silva MD, et al: A prostate-specific membrane antigen-targeted monoclonal antibody-chemo therapeutic conjugate designed for the treatment of prostate cancer. *Cancer Res* **64**: 7995–8001, 2004.
30. Marks JD: Selection of internalizing antibodies for drug delivery. *Methods Mol Biol* **248**: 201–208, 2004.
31. Marks JD, Ouwehand WH, Bye JM, et al: Human antibody fragments specific for human blood group antigens from a phage display library. *Biotechnology (NY)* **11**: 1145–1149, 1993.
32. Ellington AD, and Szostak JW: In vitro selection of RNA molecules that bind specific ligands. *Nature* **346**: 818–822, 1990.
33. Tuerk C, and Gold L: Systematic evolution of ligands by exponential enrichment: RNA ligands to bacteriophage T4 DNA polymerase. *Science* **249**: 505–510, 1990.
34. Jayasena SD: Aptamers: an emerging class of molecules that rival antibodies in diagnostics. *Clin Chem* **45**: 1628–1650, 1999.
35. Hicke BJ, and Stephens AW: Escort aptamers: a delivery service for diagnosis and therapy. *J Clin Invest* **106**: 923–928, 2000.
36. White RR, Sullenger BA, and Rusconi CP: Developing aptamers into therapeutics. *J Clin Invest* **106**: 929–934, 2000.
37. Blank M, Weinschenk T, Priemer M, et al: Systematic evolution of a DNA aptamer binding to rat brain tumor microvessels. Selective targeting of endothelial regulatory protein pigpen. *J Biol Chem* **276**: 16464–16468, 2001.
38. Morris KN, Jensen KB, Julin CM, et al: High affinity ligands from in vitro selection: complex targets. *Proc Natl Acad Sci USA* **95**: 2902–2907, 1998.
39. Farokhzad OC, Cheng J, Teply BA, et al: Targeted nanoparticle-aptamer bioconjugates for cancer chemotherapy in vivo. *Proc Natl Acad Sci USA* **103**: 6315–6320, 2006.
40. Santini JT Jr, Cima MJ, and Langer R: A controlled-release microchip. *Nature* **397**: 335–338, 1999.
41. Santini JT Jr, Richards AC, Scheidt RA, et al: Microchip technology in drug delivery. *Ann Med* **32**: 377–379, 2000.
42. Whitesides GM, Ostuni E, Takayama S, et al: Soft lithography in biology and biochemistry. *Annu Rev Biomed Eng* **3**: 335–373, 2001.
43. Kristo B, Liao JC, Neves HP, et al: Microelectromechanical systems in urology. *Urology* **61**: 883–887, 2003.
44. Li Y, Ho Duc HL, Tyler B, et al: In vivo delivery of BCNU from a MEMS device to a tumor model. *J Control Release* **106**: 138–145, 2005.
45. Grayson AC, Voskerician G, Lynn A, et al: Differential degradation rates in vivo and in vitro of biocompatible poly(lactic acid) and poly(glycolic acid) homo- and co-polymers for a polymeric drug-delivery microchip. *J Biomater Sci Polym Ed* **15**: 1281–1304, 2004.
46. Richards Grayson AC, Choi IS, Tyler BM, et al: Multi-pulse drug delivery from a resorbable polymeric microchip device. *Nat Mater* **2**: 767–772, 2003.
47. Leoni L, and Desai TA: Micromachined biocapsules for cell-based sensing and delivery. *Adv Drug Deliv Rev* **56**: 211–229, 2004.
48. Chovan T, and Guttman A: Microfabricated devices in biotechnology and biochemical processing. *Trends Biotechnol* **20**: 116–122, 2002.
49. Takeuchi S, Ziegler D, Yoshida Y, et al: Parylene flexible neural probes integrated with microfluidic channels. *Lab Chip* **5**: 519–523, 2005.
50. Xie J, Shih J, Lin Q, et al: Surface micromachined electrostatically actuated micro peristaltic pump. *Lab Chip* **4**: 495–501, 2004.



Video Clips cited in this article can be found on the internet at: <http://www.goldjournal.net>